

Switching On Magnetism in Ni-doped Graphene

E. J. G. Santos,^{1,2,*} A. Ayuela,^{1,2,†} S. B. Fagan,³ J. Mendes Filho,⁴
D. L. Azevedo,⁵ A. G. Souza Filho,⁴ and D. Sánchez-Portal^{1,2,‡}

¹ Centro de Física de Materiales, Centro Mixto CSIC-UPV/EHU, Apdo. 1072, 20080 San Sebastián, Spain

² Donostia International Physics Center (DIPC),

Paseo Manuel de Lardizabal 4, 20018 San Sebastián, Spain

³ Área de Ciências Naturais e Tecnológicas, Centro Universitário Franciscano, Santa Maria-RS, 97010-032, Brazil

⁴ Departamento de Física, Universidade Federal do Ceará, Fortaleza-CE, 60455-760, Brazil

⁵ Universidade Federal do Maranhão, São Luis-MA, 65080-040, Brazil

(Dated: September 17, 2008)

Magnetic properties of graphenic carbon nanostructures, relevant for future spintronic applications, depend crucially on doping and on the presence of defects. In this paper we study the magnetism of the recently detected substitutional Ni (Ni_{sub}) impurities. Ni_{sub} defects are non-magnetic in flat graphene and develop a non-zero magnetic moment only in metallic nanotubes. This surprising behavior stems from the peculiar curvature dependence of the electronic structure of Ni_{sub} . A similar magnetic/non-magnetic transition of Ni_{sub} can be expected by applying anisotropic strain to a flat graphene layer.

PACS numbers: 75.75.+a, 73.22.-f, 73.20.Hb, 81.05.Uw

I. INTRODUCTION

Graphenic carbon nanostructures have opened new research routes in nanoelectronics.^{1,2} In particular, their magnetic properties are receiving much attention, both experimental and theoretically, mainly in relation to spintronics. Spin-qubits and other spintronic devices seem feasible due to the very long spin relaxation and decoherence times in graphene,^{3,4} and to the fact that the magnetism of the edge states of graphenic nanoribbons can be controlled by applying external electric fields.^{5,6} Magneto-optical properties are also being actively studied.^{2,7} All these properties are drastically influenced by the presence of defects and dopants.^{8,9} For example, strong magnetic signals in nanocarbons have been reported after irradiation that seem to be associated with the creation of defects.^{10,11,12,13} Thus, the magnetic and transport properties of carbon systems can in principle be engineered using these additional degrees of freedom.

In a recent x-ray adsorption study, Ushiro *et al.*¹⁴ have demonstrated the presence of important amounts of substitutional Ni (Ni_{sub}) impurities in purified carbon nanostructures synthesized using Ni containing catalyst. Such Ni_{sub} impurities were also observed by Banhart *et al.*¹⁵ in electron microscopy images of onion-like graphenic particles. In general, due to the stability of the substitutional configuration, the incorporation of transition metals to the carbon layer during growth or saturating existing vacancies seems a likely process. In spite of this, the magnetic properties of substitutional transition-metal impurities in graphenic systems have not been studied in detail. Instead, most theoretical studies have focused on adsorbed transition-metal atoms on fullerenes and single-walled carbon nanotubes (SWCNTs).^{16,17,18,19,20,21} Few calculations to date have considered Ni_{sub} impurities^{15,22} and little attention was paid to the magnetic properties.

In this paper we present a first-principles density func-

tional theory (DFT) study of Ni_{sub} defects in graphene and armchair and zigzag SWCNTs of different diameters. We have discovered that the magnetic moment of substitutionally Ni-doped graphene can be controlled by applying mechanical deformations that break the hexagonal symmetry of the layer, like curvature does. Surprisingly, Ni_{sub} impurities are non-magnetic in flat graphene. However, their magnetic moment can be switched on by applying curvature to the structure. Furthermore, the magnetic moment of Ni_{sub} also becomes a signature of the metallicity of the structure: only metallic tubes develop a moment that depends on the tube diameter and Ni concentration. This behavior stems from the peculiar curvature dependence of the electronic structure of the Ni_{sub} impurity.

II. METHODOLOGY

Our calculations have been performed with the SIESTA code^{23,24,25} using the generalized gradient approximation (GGA)²⁶ to DFT and Troullier-Martins²⁷ pseudopotentials. Our Ni pseudopotential includes a pseudo-core with a core matching radius of 0.53 a.u. in order to perform non-linear core corrections for the description of exchange and correlation.²⁸ We have tested that this pseudopotential yields the correct magnetic moment and band structure for bulk Ni. We have used an *energy shift*²⁴ of 50 meV to define the radii of the different orbitals. A double- ζ polarized (DZP) basis set has been used for the calculation of the magnetic moments and electronic band structures of all our systems. However, we have checked that a double- ζ (DZ) basis yields to almost identical relaxed structures as the DZP basis and, therefore, we have used the smaller DZ basis for the relaxations of systems containing more than ~ 100 atoms (our supercells contain up to 512 atoms, see Fig. 5 below). Atomic coordinates

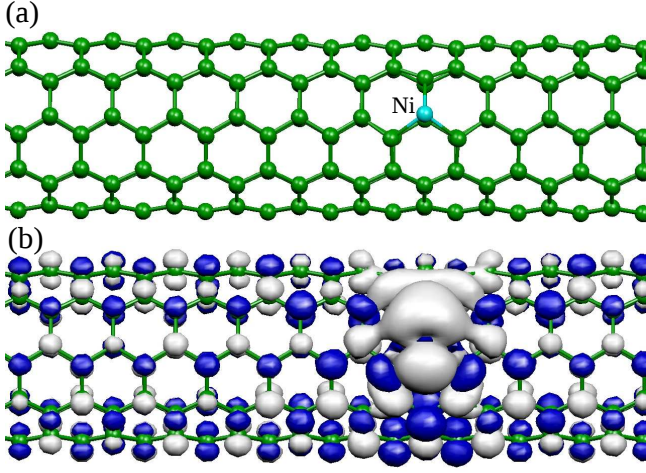


FIG. 1: (Color online) (a) Relaxed geometry of a substitutional Ni (Ni_{sub}) impurity in a (5,5) SWCNT, and (b) iso-surface ($\pm 0.004 \text{ e}^-/\text{Bohr}^3$) of the magnetization density with light (gray) and dark (blue) surfaces corresponding, respectively, to majority and minority spin.

were relaxed using a conjugated gradient algorithm until all force components were smaller than $0.05 \text{ eV}/\text{\AA}$. Relevant lattice parameters were fixed to those of the pristine systems. To prevent spurious interactions the minimum distance between the walls of neighboring SWCNTs was $18 \text{ \AA}$. The fineness of the real-space grid used to calculate the Hartree and exchange-correlation contribution to the total energy and Hamiltonian was equivalent to a 180 Ry plane-wave cutoff. A good integration over the Brillouin zone proved to be instrumental to converge the magnetic moment of Ni_{sub} impurities in metallic SWCNTs. The k -point sampling was equivalent to a 136×136 sampling²⁹ of the Brillouin zone of graphene. We used a Fermi-Dirac distribution with $k_B T = 21 \text{ meV}$. In some cases we have checked that our results are reproduced using a different methodology: the VASP code with projected-augmented-wave potentials and a plane-wave cut-off energy of 400 eV .^{30,31}

III. RESULTS AND DISCUSSION

Figure 1 (a) illustrates the typical equilibrium structure of Ni_{sub} in the case of a (5,5) SWCNT. The Ni atom appears displaced $\sim 0.9 \text{ \AA}$ from the carbon plane. Although both outward and inward displacements can be stabilized, the outward configuration is always more stable. The calculated Ni-C distances (d_{NiC}) are in the range $1.77\text{--}1.85 \text{ \AA}$ in agreement with experiment^{14,15}. Armchair tubes exhibit two slightly shorter and one larger values of d_{NiC} , the opposite happens for (n,0) tubes, whereas for graphene we obtain a threefold symmetric structure with $d_{\text{NiC}} = 1.78 \text{ \AA}$. Ni adsorption inhibits the reconstruction³² of the carbon vacancy. Fur-

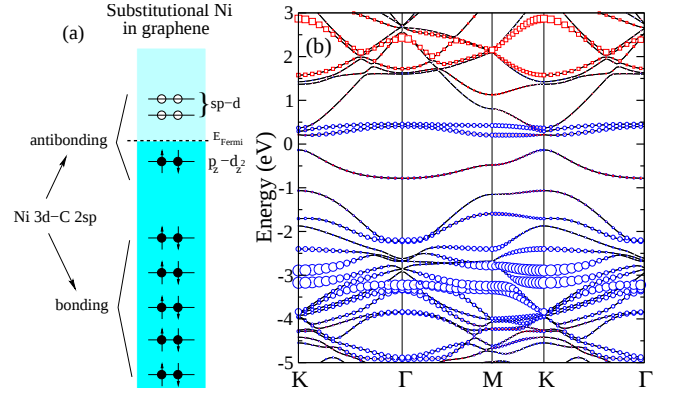


FIG. 2: (Color online) (a) Schematic representation of the electronic structure of a Ni_{sub} impurity in graphene. Panel (b) shows the calculated band structure for a Ni_{sub} impurity in a 4×4 graphene supercell. The size of the circles and squares corresponds to the amount of Ni $3d$ and $4s$ character respectively. Energies are referred to the Fermi energy.

thermore, we have checked that a symmetric structure is obtained even when starting from a relaxed vacancy. The Ni binding energy is quite large: 7.9 eV for graphene and about 8.5 eV for (5,5) and (8,0) tubes. The calculated adsorption energy of Ni on the surface of the same tubes is $\sim 2.5 \text{ eV}$.²⁰ Thus, we can conclude that the formation of Ni_{sub} defects by passivation of existing carbon vacancies is a very likely process both for graphene and for SWCNTs.

Figure 1 (b) shows the magnetization density for a Ni_{sub} defect in a (5,5) metallic nanotube at large dilution (0.3 % Ni concentration). The total magnetic moment of this system is $0.5 \mu_B$. The magnetization comprises the Ni atom and its C neighbors. However, it also extends considerably along the tube, particularly in the direction perpendicular to the tube axis. This indicates the polarization of some of the delocalized electronic states in the nanotube. Indeed, as we clarify below, the magnetism in substitutionally Ni-doped SWCNTs only appears associated with the curvature and the metallicity of the host structure

Figure 2 (a) shows a scheme of the electronic structure of Ni_{sub} in graphene, while Fig. 2 (b) presents the calculated band structure using a 4×4 supercell. Very similar results are obtained using larger supercells.³³ Several levels with Ni-C bonding character and a strong Ni $3d$ contribution can be found between 2 and 6 eV below the Fermi energy (E_F). This considerable band width is a signature of the strong Ni-C interaction. As a consequence of the bonding interaction the Ni $3d$ band is stabilized and can be pictured as “fully occupied”. Close to E_F we find three levels with Ni-C antibonding character. One of them is occupied and appears around 0.7 eV below E_F close to Γ . This level comes from a fully symmetric linear combination of the $2p_z$ orbitals (z -axis normal to the layer) of the nearest C neighbors interacting with the $3d_{z^2}$ orbital of Ni. Two levels coming from the hybridiza-

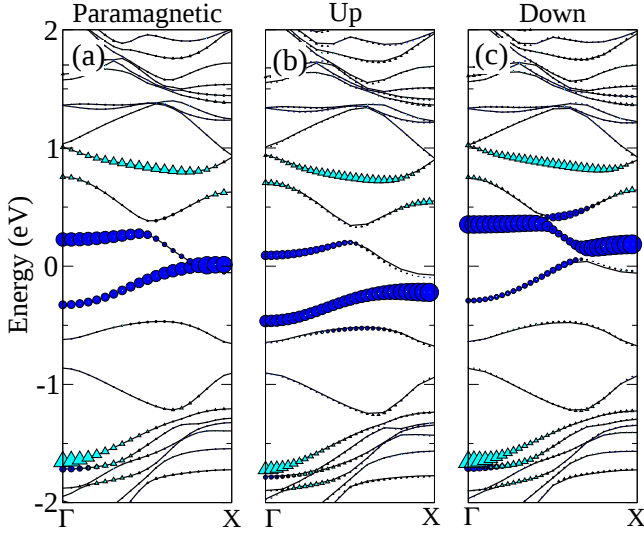


FIG. 3: (Color online) Band structure of a (5,5) nanotube containing a Ni impurity every 4 unit cells ($\text{Ni}_{\text{sub}}\text{-Ni}_{\text{sub}}$ distance of ~ 9.8 Å) for (a) a paramagnetic calculation, and for (b) majority and (c) minority spins. Circles and triangles correspond respectively to the amount of Ni $3d_{yz}$ and $3d_{xz}$ character. X-axis is parallel to the tube axis and y-axis is tangential.

tion of the in-plane sp lobes of the carbon neighbors with the Ni $3d_{xz}$ and $3d_{yz}$ orbitals appear ~ 0.5 eV above E_F .

As a consequence of this electronic structure, with the Ni $3d$ states well below E_F and no flat bands crossing E_F , the magnetic moment of the Ni_{sub} impurity in graphene is zero. Interestingly, the three levels appearing close to E_F in Fig. 2 are reminiscent of those found for the unreconstructed carbon vacancy in graphene³². The presence of a Ni atom stabilizes such symmetric structure of the vacancy and slightly shifts the two levels coming from the sp lobes (now C $2sp\text{-Ni } 3d$ antibonding levels) to higher energies. This contributes to stabilize the paramagnetic solution and renders a Ni_{sub} impurity with zero spin polarization in the flat layer of graphene.

The basic picture described above is still valid for the electronic structure of the Ni_{sub} impurity in SWCNTs. However, the modifications that appear due to the curvature of the carbon layer are responsible for the appearance of a magnetic moment. Figure 3 (a) shows the band structure of a paramagnetic calculation of a (5,5) SWCNT with a Ni_{sub} impurity every four unit cells. Here the distance between neighboring Ni_{sub} impurities is similar to that of the graphene layer in Fig. 2 (b), although the Ni concentration is 2.5 times lower (1.3 %). Comparing these two Figures we can appreciate the effects of curvature. The degeneracy between d_{xz} and d_{yz} states is removed (x-axis taken along the tube axis and y-axis along the tangential direction at the Ni site). The d_{yz} contribution is stabilized by several tenths of eV and a quite flat band with strong d_{yz} character is found *pinned* at E_F close to the Brillouin-zone boundary. Under these

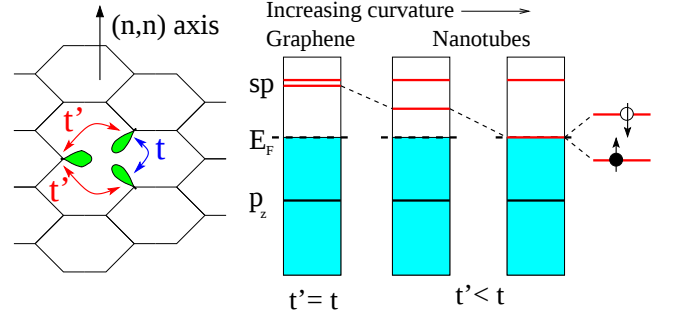


FIG. 4: (Color online) Effect of curvature (anisotropic strain) on Ni_{sub} in (n,n) tubes. The electronic structure of Ni_{sub} is similar to that of the unreconstructed carbon vacancy. One of the impurity levels with antibonding C $2sp\text{-Ni } 3d$ character is shifted downwards and, for large enough curvatures, becomes partially populated and spin-polarized.

conditions the spin-compensated solution becomes unstable and a magnetic moment of $0.48 \mu_B$ is developed. Figures 3 (b) and (c) show, respectively, the band structure for majority and minority spins. The exchange splitting of the d_{yz} level is ~ 0.4 eV and the energy gain with respect to the paramagnetic solution is 32 meV. Similar results are obtained using the VASP code.

In general, whenever a flat impurity with appreciable Ni $3d$ character becomes partially filled we can expect the appearance of a magnetic moment. The population of such an impurity level occurs at the expense of the simultaneous depopulation of some of the delocalized carbon p_z levels of the host structure. For this reason the development of a magnetic moment is more likely for Ni_{sub} impurities in metallic structures like the armchair tubes. The crucial role of the host states also explains the delocalized character of the magnetization density depicted in Fig. 1 (b). However, it is important to stress that the driving force for the formation of a magnetic moment associated with the Ni_{sub} impurity in a SWCNT is the local curvature of the carbon layer that shifts the energy position of one of the impurity levels downwards until it crosses E_F . A schematic representation of this phenomenon can be found in Fig. 4 where we also emphasize the similarities between the levels of the Ni_{sub} defect and those of the unreconstructed carbon vacancy. At large tube diameters we must recover the limit of flat graphene with zero magnetic moment.

For semiconducting tubes the situation is somewhat different. The d_{xz} and d_{yz} derived levels will remain unoccupied unless their energies are shifted by a larger amount that pushes one of them below the top of the valence band. Therefore, if the tube has a large enough gap the magnetic moment will be zero irrespective of the tube diameter. We have explicitly checked that a zero magnetic moment is obtained for (8,0) and (10,0) semiconducting tubes for Ni concentrations ranging from 1.5% to 0.5%. The different magnetic behavior of Ni_{sub} impurities depending on the metallic and semiconducting character of the host structure provides a route to exper-

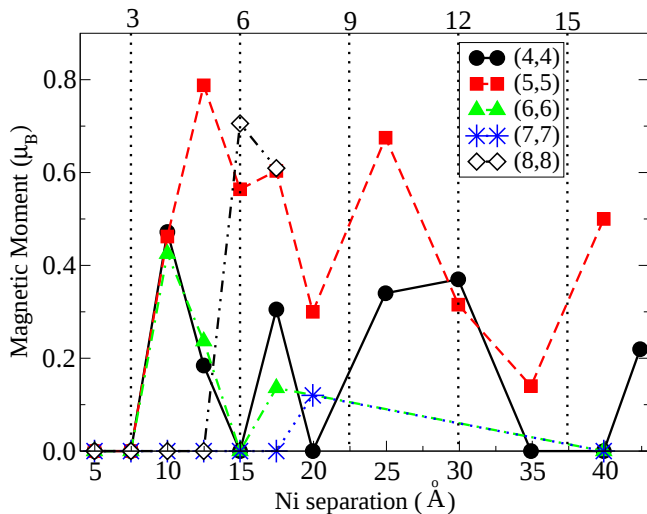


FIG. 5: (Color online) Magnetic moment per Ni impurity for different (n,n) tubes as a function of the distance between periodic images of the impurity, i.e., the length of the supercell. The vertical lines and the numbers at the top indicate the number of unit cells in a supercell of a given length.

imentally identify metallic armchair tubes.

Figure 5 displays the magnetic moment per Ni_{sub} atom for Ni-doped armchair tubes of different diameters. All of them present a magnetic moment that oscillates as a function of the tube diameter and the size of the supercell used in the calculation, i.e., the $\text{Ni}_{\text{sub}}\text{-Ni}_{\text{sub}}$ distance. For (4,4), (5,5) and (6,6) tubes the first supercell showing a non-zero magnetic moment contains four unit cells. For (7,7) and (8,8) tubes this minimum length increases up to eight and six unit cells, respectively. The appearance of a complex oscillatory pattern as a function of the $\text{Ni}_{\text{sub}}\text{-Ni}_{\text{sub}}$ distance is easily understood if we recall that the magnetic moment critically depends on the energy position of a particular impurity level nearby E_F and the strong hybridization of this level with the delocalized states of the nanotube. Another consequence of this hybridization is the long range of the interaction between Ni_{sub} impurities: for example, the magnetic moment in (5,5) and (4,4) tubes still presents strong oscillations in a range of $\text{Ni}_{\text{sub}}\text{-Ni}_{\text{sub}}$ distances between 20 and 40 Å. Unfortunately, a meaningful exploration of larger distances between impurities requires a methodology different from the *ab initio* supercell approach used here.

Finally, we have examined the magnetic coupling between Ni_{sub} impurities in the (5,5) tube. We have doubled some of the simulation cells considered above, so they contain two Ni atoms, and calculated ferromagnetic (FM) and antiferromagnetic (AFM) arrangements. Only when the two Ni_{sub} impurities shared a common C neighbor the AFM arrangement was favored by a few meV. FM configurations were the most stable in all other cases. Although more work is necessary to accurately determine the size and distance dependence of the effective exchange interaction (probably using model calculations similar to

those in Ref. 34), our results indicate that Ni_{sub} impurities in small diameter metallic nanotubes, where they develop a magnetic moment, can exhibit relatively large FM couplings that slowly decay with distance. For example, for Ni_{sub} impurities at distances of 10 Å in a (5,5) tube we estimate a J_{eff} of ~ 9 meV. This FM interactions can have important implications for the experimental detection of the curvature dependent magnetism of the Ni_{sub} impurities described in this work and its influence in the observation of magnetism in carbon nanotube samples.

IV. CONCLUSIONS

The calculations presented here show that substitutional Ni impurities in graphenic carbon structures present a strong covalent interaction with their carbon neighbors. This interaction stabilizes the 3d levels of Ni that appear as a completely filled shell. As a consequence, Ni_{sub} is non-magnetic in graphene. Two unoccupied levels of the Ni_{sub} impurity appear close to E_F corresponding to antibonding combinations of Ni 3d orbitals and C 2sp lobes. Curvature breaks the degeneracy of these two levels and, under appropriate conditions, shifts one of them to lower energies such that becomes partially occupied in metallic armchair tubes. In this situation the system develops a magnetic moment that exhibits a complex behavior as a function of the tube diameter and Ni concentration. However, for semiconducting zigzag tubes the Ni_{sub} impurities remain non-magnetic. These results should be taken into account when studying the magnetic properties of carbon nanostructures.

In summary, curvature can be used to drive substitutional Ni impurities between a magnetic and a non-magnetic state in metallic graphenic carbon nanostructures. In particular, the magnetic properties of substitutionally Ni-doped graphene can be tuned by controlling the curvature of the layer around the Ni_{sub} defects. A possible way to do this is to deposit the graphene layer on a substrate with a small lattice parameter mismatch. This can cause the undulation and local bending of the graphene layer^{35,36}. Alternatively, a similar non-magnetic/magnetic transition of Ni_{sub} might be obtained applying anisotropic strain to a flat graphene layer. In this regard, we are currently exploring if the formation of a magnetic moment can also be controlled by applying uniaxial strain to a flat Ni_{sub} -doped graphene layer.

Acknowledgments

EJGS, AA and DSP acknowledge support from the Basque Government and UPV/EHU (Grant No. IT-366-07), CSIC, the Spanish MEC (Grant No. FIS2007-66711-C02-02), and the Basque Government and Diputación Foral de Guipuzcoa through the ETORTEK program.

-
- * Electronic address: eltonjose.gomes@ehu.es
† Electronic address: swxayfea@ehu.es
‡ Electronic address: sqbsapod@ehu.es
- ¹ A. K. Geim and K. S. Novoselov, *Nature Mat.* **6**, 183 (2007).
 - ² A. Jorio, M. S. Dresselhaus, and G. Dresselhaus, eds., *Carbon Nanotubes: Advanced Topics in the Synthesis, Structure, Properties and Applications* (Springer-Verlag, Berlin, 2008).
 - ³ L. E. Hueso, J. M. Pruneda, V. Ferrari, G. Burnell, J. P. Valdés-Herrera, B. D. Simons, P. B. Littlewood, E. Artacho, A. Fert, and N. D. Mathur, *Nature* **445**, 410 (2007).
 - ⁴ B. Trauzettel, D. V. Bulaev, D. Loss, and G. Burkard, *Nature Phys.* **3**, 192 (2007).
 - ⁵ Y.-W. Son, M. L. Cohen, and S. G. Louie, *Nature* **444**, 347 (2006).
 - ⁶ O. V. Yazyev and M. I. Katsnelson, *Phys. Rev. Lett.* **100**, 047209 (2008).
 - ⁷ S. Zaric et al., *Phys. Rev. Lett.* **96**, 016406 (2006).
 - ⁸ B. Uchoa, V. N. Kotov, N. M. R. Peres, and A. H. Castro Neto, *Phys. Rev. Lett.* **101**, 026805 (2008).
 - ⁹ L. Brey, H. A. Fertig, and S. Das Sarma, *Phys. Rev. Lett.* **99**, 116802 (2007).
 - ¹⁰ P. O. Lehtinen, A. S. Foster, A. Ayuela, A. Krasheninnikov, K. Nordlund, and R. M. Nieminen, *Phys. Rev. Lett.* **91**, 017202 (2003).
 - ¹¹ P. Esquinazi, D. Spemann, D. Höhne, A. Setzer, K.-H. Han, and T. Butz, *Phys. Rev. Lett.* **91**, 227201 (2003).
 - ¹² P. O. Lehtinen, A. S. Foster, Y. Ma, A. V. Krasheninnikov, and R. M. Nieminen, *Phys. Rev. Lett.* **93**, 187202 (2004).
 - ¹³ A. V. Krashinnikov and F. Banhart, *Nature Mat.* **6**, 723 (2007).
 - ¹⁴ M. Ushiro, K. Uno, T. Fujikawa, Y. Sato, K. Tohji, F. Watari, W. J. Chun, Y. Koike, and K. Asakura, *Phys. Rev. B* **73**, 144103 (2006).
 - ¹⁵ F. Banhart, J. C. Charlier, and P. M. Ajayan, *Phys. Rev. Lett.* **84**, 686 (2000).
 - ¹⁶ Y.-H. Lee, S. G. Kim, and D. Tománek, *Phys. Rev. Lett.* **78**, 2393 (1997).
 - ¹⁷ A. Ayuela, G. Seifert, and R. Schmidt, *Z. Phys. D* **41**, 69 (1997).
 - ¹⁸ G. Seifert et al., *Appl. Phys. A* **66**, 265 (1998).
 - ¹⁹ M. Menon, A. N. Andriotis, and G. E. Froudakis, *Chem. Phys. Lett.* **320**, 425 (2000).
 - ²⁰ E. Durgun, S. Dag, V. M. K. Bagci, O. Gülseren, T. Yildirim, and S. Ciraci, *Phys. Rev. B* **67**, 201401(R) (2003).
 - ²¹ Y. Yagi, T. M. Briere, M. H. F. Sluiter, V. Kumar, A. A. Farajian, and Y. Kawazoe, *Phys. Rev. B* **69**, 075414 (2004).
 - ²² A. N. Andriotis, M. Menon, and G. E. Froudakis, *Phys. Rev. Lett.* **85**, 3193 (2000).
 - ²³ D. Sánchez-Portal, P. O. E. Artacho, and J. M. Soler, *Int. J. Quantum Chem.* **65**, 453 (1997).
 - ²⁴ J. M. Soler, E. Artacho, J. D. Gale, A. García, J. Junquera, P. Ordejón, and D. Sánchez-Portal, *J. Phys.: Condensed Matter* **14**, 2745 (2002).
 - ²⁵ D. Sánchez-Portal, P. Ordejón, and E. Canadell, *Structure and Bonding* **113**, 103 (2004).
 - ²⁶ J. P. Perdew, K. Burke, and M. Ernzerhof, *Phys. Rev. Lett.* **77**, 3865 (1996).
 - ²⁷ N. Troullier and J. L. Martins, *Phys. Rev. B* **43**, 1993 (1991).
 - ²⁸ S. G. Louie, S. Froyen, and M. L. Cohen, *Phys. Rev. B* **26**, 1738 (1982).
 - ²⁹ H. J. Monkhorst and J. D. Pack, *Phys. Rev. B* **13**, 5188 (1976).
 - ³⁰ G. Kresse and J. Hafner, *Phys. Rev. B* **47**, 558 (1993).
 - ³¹ G. Kresse and D. Joubert, *Phys. Rev. B* **59**, 1758 (1999).
 - ³² H. Amara, S. Latil, V. Meunier, P. Lambin, and J.-C. Charlier, *Phys. Rev. B* **76**, 115423 (2007).
 - ³³ Because of the quite symmetric position of the Ni atom over the C vacancy the $3d_{xz}$ and $3d_{yz}$ derived bands are almost degenerate at Γ . In spite of the relatively large distance between Ni atoms in the 4×4 graphene supercell (~ 9.8 Å), these bands show a considerable dispersion of ~ 0.2 eV. The large range of the $\text{Ni}_{\text{sub}}\text{-Ni}_{\text{sub}}$ interaction is a signature of the strong hybridization of the impurity levels with the states of the carbon layer. Another signature of this hybridization is the gap of ~ 0.5 eV that opens in the graphene layer around K. Using a larger 8×8 supercell i.e., increasing the $\text{Ni}_{\text{sub}}\text{-Ni}_{\text{sub}}$ distance to ~ 19.7 Å, the width of the impurity bands and the gap decrease, respectively, to ~ 20 meV and ~ 100 meV. The positions of the impurity bands are, however, very similar to the case of the smaller cell.
 - ³⁴ D. F. Kirwan, C. G. Rocha, A. T. Costa, and M. S. Ferreira, *Phys. Rev. B* **77**, 085432 (2008).
 - ³⁵ A. T. N'Diaye, S. Bleikamp, P. J. Feibelman, and T. Michely, *Phys. Rev. Lett.* **97**, 215501 (2006).
 - ³⁶ P. J. Feibelman, *Phys. Rev. B* **77**, 165419 (2008).